

fax +48 71 372 61 11

mail: info@rawlplug.com

51-416 Wrocław Poland


# **VOC Emission Test report**

## 1. Sample information

Sample identification	KEM-PSF-300-KOE			
Product type	Polyester styrene free resin			
Testing laboratory	Environmental Protection and Wood Chemistry Department of			
Testing laboratory	Wood Technology Institute			
Report identification number	U-405-BOŚ/2013			
Sample delivered	10.12.2013			
Test start, duration	13.12.2013, 28 days			

## 2. Resulting VOC Emission Class Label

Recommendation based on French regulation as published on 25<sup>th</sup> March 2011 (décret DEVL1101903D) and on 13<sup>th</sup> May 2011 (arête DEVL 1104875A).

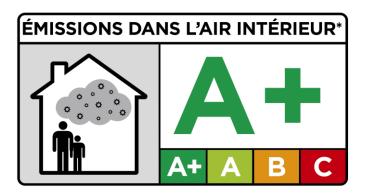

#### 3. Conclusion on CMR substances emission

Product fulfills the requirements of the French regulation published on 30<sup>th</sup> April 2009 (DEVP 0908633A) and DEVP 0910046A published on 28<sup>th</sup> May 2009.

#### 4. Test method



Raiffeisen Bank Polska SA o/Wrocław 49 1750 1064 0000 0000 0106 5211

Kapitał zakładowy: 32.560.000 PLN Kapitał wpłacony: 32.560.000 PLN



Ul. Kwidzyńska 6 51-416 Wrocław Poland

tel. +48 71 326 01 00 fax +48 71 372 61 11 mail: info@rawlplug.com

Wrocław, 21. 01.2014

Test was carried out in accordance with following ISO standards: 16000-6, -9, -11 using gas chromatography/mass spectroscopy as principle.

## Chromatographic analysis conditions:

Chromatograph	Trace 2000 Thermoquest/Finnigan
Column:	DB-624 MS
- diameter	0,25 mm
- film thickness	1,4 μm
- length	30 m
Temperature program	$35^{\circ}$ C (4 min) $5^{\circ}$ C/min $\rightarrow$ 140°C (0 min)
	$12^{\circ}$ C/min $\rightarrow$ 230°C (3 min)
Feeder	Thermal desorber – Master TD, 270°C
Carrier gas	Helium (100 kPa)
Detector	MS 220°C

## Test chamber parameter:

Chamber volume	0,225 m <sup>3</sup>	Temperature	23 ± 2°C	Relative humidity	50 ± 5%
Air change rate	0,5 h <sup>-1</sup>	Loading ratio	0,007 m <sup>2</sup> /m <sup>3</sup>	Area specific air exchange rate	0,5 m <sup>3</sup> /m <sup>2</sup> ·h

Sample dimensions:  $30 \times 27 \times 5$  mm; One sample in Test chamber.

## 5. Results

NIP: 895 16 87 880 KRS: 0000033537

Raiffeisen Bank Polska SA o/Wrocław 49 1750 1064 0000 0000 0106 5211

Kapitał zakładowy: 32.560.000 PLN Kapitał wpłacony: 32.560.000 PLN

www.rawlplug.com



Ul. Kwidzyńska 6 51-416 Wrocław Poland

tel. +48 71 326 01 00 fax +48 71 372 61 11 mail: info@rawlplug.com

Wrocław, 21. 01.2014

# Compounds to be monitored to determine VOC emission class label:

Substance	Concentration after 28 days [μg/m³]	С	В	Α	A+
Formaldehyde	No emission recorded	> 120	< 120	< 60	< 10
Acetaldehyde	No emission recorded	> 400	< 400	< 300	< 200
Toluene	No emission recorded	> 600	< 600	< 450	< 300
Tetrachloroethylene	No emission recorded	> 500	< 500	< 350	< 250
Xylene	No emission recorded	> 400	< 400	< 300	< 200
1,2,4-trimethylbenzene	No emission recorded	> 2000	< 2000	< 1500	< 1000
1,4-dichlorobenzene	No emission recorded	> 120	< 120	< 90	< 60
Ethylbenzene	No emission recorded	> 1500	< 1500	< 1000	< 750
2-butoxyethanol	No emission recorded	> 2000	< 2000	< 1500	< 1000
Styrene	No emission recorded	> 500	< 500	< 350	< 250
TVOC		> 2000	< 2000	< 1500	< 1000
CMR compounds					
Benzene	No emission recorded	<1			
Dibuthylphthalate (DBP)	No emission recorded				
Diethylhexylphthalate (DEHP)	No emission recorded				

NIP: 895 16 87 880 KRS: 0000033537

Raiffeisen Bank Polska SA o/Wrocław 49 1750 1064 0000 0000 0106 5211

Kapitał zakładowy: 32.560.000 PLN Kapitał wpłacony: 32.560.000 PLN

www.rawlplug.com